

US EPA ARCHIVE DOCUMENT

GeoSyntec Consultants

## ALTERNATIVES TO SECONDARY CONTAINMENT LINING

Corresponding Author: Tarik Hadj-Hamou, Ph.D., P.E.<sup>(1)</sup>

Phil Myers, P.E.<sup>(2)</sup>

Thierry Sanglerat, P.E.<sup>(3)</sup>

### ABSTRACT

Federal regulations for the performance of secondary containment system for Aboveground Storage Tanks (AST) at bulk storage facilities states in 40 CFR §112.7(e)(2)(ii), that, “*all bulk storage tank installations should be constructed so that a secondary means of containment is provided for the entire contents of the largest tank plus sufficient freeboard to allow for precipitation. Diked areas should be sufficiently impervious to contain spilled oil.*” State requirements for the performance of secondary containment range from no specific requirements to specified numerical values for design (e.g., hydraulic conductivity, time to control and clean). While it is often assumed that building or retrofitting a secondary containment requires installation of synthetic liners, engineering alternatives exist that may provide equivalent or better protection of the environment.

This paper presents a methodology for selecting the optimum engineering alternative to retrofit secondary containments at bulk storage facilities. In the context of this paper, optimum engineering alternative is defined as the cost-effective engineering alternative that provides the required level of protection of the environment and meets operational constraints. The methodology is based on statistical analyses of failure and releases, risk analysis, and performance analysis.

The methodology is applied to an existing tank farm located inland and above the groundwater table. It is shown that, for this tank farm, optimum protection of the environment can be achieved with the installation of double bottoms, proper overfill

---

(1) Associate, GeoSyntec Consultants, 2100 Main Street, Suite 150, Huntington Beach, CA 92648  
(714) 969-0800 – THadj-Hamou@GeoSyntec.com

(2) Senior Standard Engineer, Chevron Products Company, 6001 Bollinger Canyon Road, P.O. Box 6004, San Ramon, CA  
(925) 842-2288 – PEMY@chevron.com

(3) Executive Vice President, GeoSyntec Consultants, 2100 Main Street, Suite 150, Huntington Beach, CA 92648  
(714) 969-0800 – TSanglerat@GeoSyntec.com

prevention, and a perimeter catchment system around the tanks rather than through the installation of synthetic liners.

## INTRODUCTION

The United States (US) Environmental Protection Agency (EPA) estimated in 1996 that approximately 502,000 facilities have Aboveground Storage Tanks (AST) and store significant quantities of oil in bulk. A typical facility consists of one or more AST. At most of these facilities, the AST are within a secondary containment area.

Historically, secondary containment areas have been built to provide horizontal confinement of the hypothetical spill. The design was governed by fire codes rather than environmental concerns. Consequently, the quality of the secondary containment system varies greatly and range from dikes built out of locally available soil to concrete walls [Figure 1]. The secondary containment area must contain the volume of the largest tank plus reasonable precipitation.

However, in recent years, concern has been the downward migration of product spilled in the secondary containment areas to groundwater and the lack of liners in the secondary containment areas. The USEPA (USEPA, 1996) estimates that approximately 84 percent of the AST facilities do not have impervious liners in the secondary containments.

Considering that a review of discharge data reported by the USEPA (USEPA 1996) indicated that 30 percent of reported oil discharges are to secondary containment areas, there has been an increase in regulatory pressure for requiring the installation of impervious liners in secondary containment areas.

Releases from ASTs may be classified into four broad categories:

- Shell Releases;
- Bottom Releases;
- Overfill; and
- Equipment/Appurtenances Leaks.

Shell releases may occur as a result of structural failure of the shell. A distinction is made between rapid shell release due to total rupture of the shell and slow shell release due to a small defect or a minor failure (cracked fitting). Rapid shell releases due to catastrophic failure of the shell are rare. One of the best known cases is the rupture of the newly repaired diesel tank at the Ashland Oil Terminal in Floreffe Allegheny County, Pennsylvania. On 2 January 1988, the tank ruptured sending releasing almost 3.9 million gallons of diesel fuel [[http://www.dep.state.pa.us/dep/pa\\_env-her/ashland.htm](http://www.dep.state.pa.us/dep/pa_env-her/ashland.htm), 2002].

Bottom releases occur through pinhole at the bottom of the tank and are mostly related to corrosion of the bottom plates. Cutter (1999) reports that a leak at a rate of 1 drop/sec will result in a total volume of 34 gallons (128.7 l) or roughly 0.8 barrels in one month.

Overfill occurs when the volume of the product received exceeds the capacity of the tank. The oil is typically released through the roof vent. Overfill are most often related to operator errors.

Equipment/appurtenance releases typically involve a defect or a failure such as cracking or a gasket failure.

The American Petroleum Institute (API) conducted an extensive review of the different types of releases and proposed a series of detection and prevention measures (API, 1997). Because of the risk of environmental impacts from releases at ASTs, regulatory changes have occurred pushing for retrofitting secondary containments.

## REGULATORY OVERVIEW

The Oil Pollution Act (OPA) was passed in 1990 and amends §311 of the Clean Water Act (CWA) to increase federal response authority and private response capability and liability. CWA §311 requires the preparation of plan to respond to worst-case discharge of oil and set forth the requirements for these plans. These requirements are detailed in a proposed revision to the Oil Pollution Prevention regulation published as Part 112 of Title 40 of the Code of Federal Regulations (40 CFR 112). In particular, §112.7 details the requirements for a Spill Prevention Control and Countermeasure Plans (SPCC

plan). Paragraph §112.7(e)(2)(ii) addresses the issue of secondary containment areas at bulk storage facilities and repairs that “*Diked areas shall be sufficiently impervious to contain spilled oil.*” The terminology *sufficiently impervious* is not defined in the regulations.

Other agencies that provide insight in the design of secondary containments are the National Fire Protection Association NFPA Code 30 (NFPA, 1993 and the EPA Liner Study, USEPA (1996). The fire code provides recommendation for height and spacing of the berms. The fire code further specifies that the dikes or berms should be liquid tight. The EPA Liner study does not make any recommendation for permeability of the liners and further specifies that the requirement should be part of a voluntary program at state level.

At the state level, a review of all state regulations indicated a wide range of requirements. Example of requirements include:

- No Liner Required: CA, IL, MA
- Sufficiently Impermeable: AK and LA
- Impervious: KS and WI
- Liquid Tight: AL and 32 Other States that follow the NFPA 30 Fire Code
- No Breakthrough Within 72 Hours: VA
- Specific Values of Hydraulic Conductivity: MD:  $1 \times 10^{-4}$  cm/sec, PA:  $1 \times 10^{-6}$  cm/sec, ID:  $1 \times 10^{-7}$  cm/sec

## RETROFITTING OPTIONS

There are two major groups of options for retrofitting an AST facility to minimize the risk of contamination of the environment by releases. The first group includes the installation of liners in the secondary containment areas or enhancing the soil in place. The second group includes the installation of environmental controls or the use of preventative measures or enhancement of the tanks. Table 1 below lists different options for each of the two groups.

**TABLE 1: RETROFITTING OPTIONS**

<b>LINER OPTIONS</b>		<b>ENVIRONMENTAL/CONTROL OPTIONS</b>	
<b>Surficial Liners</b>	<b>Enhanced Existing Soil Liner</b>	<b>Environmental Controls</b>	<b>Prevention and Enhancement</b>
Geomembrane	Biological Clogging	Slurry Walls	Double Bottoms in Tanks
Geosynthetic Clay Liner	Chemical Clogging	GW Control	Leak Detection Systems
Compacted Clay	Soil Cement		Preventative Measures
Concrete	Chemical Grouting		Backflow Prevention
Asphalt	Soil Bentonite		Overfill Prevention
Spray-On Liners			Operational and Procedural Controls

**SELECTION METHODOLOGY**

The selection methodology is a two-step process. The first step is to select the optimum liner. The second step is to select between a liner option and an environmental or enhancement option. To select, design, and implement the cost effective, technically sound and environmentally effective liner solution, a list of selection criteria was developed. The list includes criteria related to site conditions, engineering design, construction, operator issues, and cost. These criteria are listed in Table 2.

**TABLE 2: SELECTION CRITERIA FOR LINER OPTIONS**

<b>Site Conditions</b>	<b>Engineering Design</b>	<b>Construction</b>	<b>Operator Issues</b>	<b>Cost</b>
Existing Conditions	Product Compatibility	Constructability	Operation & Maintenance	Capital
Geometry	Desiccation Resistance	Availability of Materials	Operational Flexibility	Maintenance
Penetrations	Freeze-Thaw Resistance	Weather	Storm Water Management	Clean-up
Regulatory Acceptance	Temperature Extremes		Clean-up	Remediation
	Wind Resistance		Subsurface Remediation	
	Ultraviolet Resistance		Trafficability	
	Fire Resistance		Vegetation Control	

The methodology for selecting the optimum liner option is based on a ranking of the options. Each option is graded with respect to each of the selection criterion using a qualitative grade scale. The qualitative grade scale developed to rank the liner options is shown in Table 3.

**TABLE 3: GRADING SCALE**

GRADE	DEFINITION
A	Satisfactory Performance With Minimal Extra Effort
B	Satisfactory Performance if Specific Design Elements are Implemented
C	Significant Extra Effort May Be Required To Achieve Satisfactory Performance
D	Satisfactory Performance May Not Be Feasible
F	Satisfactory Performance Will Not Be Feasible

A matrix is developed summarizing site information, comments about the applicability of each criterion to each liner option, and the qualitative grade assigned to each liner option. The matrix developed for the example examined in this paper is shown in Table 4. The grades are tallied up and a ranking of the options is then established based on the total grade of each option. The top three options are then examined further to ensure that they will meet the intent of the design and meet the Owner's preferences if any.

The second step in the methodology is to compare the top-ranked liner option to a solution from the Environmental/Control group of options. This comparison is based on a risk analysis of the consequences of a spill. The risk analysis is based on an estimate of the volume of product that would be released on an annual basis to the environment under different scenarios and assuming a catastrophic failure.

To compare a liner in the secondary containment areas to a retrofitting of the tanks, the following two scenarios are examined:

- Scenario 1: Liner in the facility and single bottoms in the tanks.
- Scenario 2: No liner in the facility and double bottom in the tanks.

Under scenario 1, the volume of petroleum product,  $V_1$  that will be released to the environment when a liner is installed in the open area and the single bottoms are left unchanged is given as:

$$V_1 = (\text{Leakage Rate through Bottom}) \times (\text{Area of Bottom}) \times (\text{Time})$$

Note that it is assumed in these scenarios the bottoms have defects and/or pinholes and that the liner installed in the secondary containment does not. This latter assumption is conservative as depths in liners installed in tank farms have been observed. Defects in liners come from puncture, incomplete seams, or gaps at boots installed around pipe penetrations (Figure 2). Studies by Giroud and Bonaparte (1989) have shown that geomembrane liners installed with strict construction quality assurance could be considered to have one to two defects per acre with a diameter of 2 mm. Using electric detection surveys Laine (1991) has shown that liners installed with strict construction quality assurance could have five or more defects per acre with diameter less than 0.5 mm. In tank farms where numerous boots are installed around pipe penetrations, support, and others appurtenances it is expected that even with a very strict construction quality assurance the number of defects will exceed the numbers listed previously. The importance of these defects is very important as they lower the effectiveness of the liner to function as an impervious barrier. The role of such defect in lowering the effectiveness of liner was further demonstrated by King et al. (1997). King et al. (1997) showed that a geomembrane with a defect rate of about 2 in<sup>2</sup>/acre provided the same level of protection in the case of a catastrophic spill as a soil with a hydraulic conductivity of 10<sup>-5</sup> cm/s.

Under scenario 2, the volume of petroleum product,  $V_2$  that will be released to the environment when double bottoms are installed in each AST and the open area within the secondary containment area is left unchanged is given as:

$$V_2 = (\text{Leakage Rate through Double Bottom}) \times (\text{Area of Double Bottom}) \times (\text{Time}) + (\text{Volume of Product Infiltrated in Soil Following A Hypothetical Catastrophic Failure})$$

The better scenario is the scenario that will minimize the volume of petroleum product release to the environment over the economic life of the tank farm.

Define a performance ratio to compare the two options:

$$PR = V_1 / V_2$$

Because PR is a function of time and of the volume of product infiltrated in the soil, it will depend upon the site characteristics such as the hydraulic conductivity of the soil, and will range from values less than one to values greater than 1. PR equals to 1 indicates that the two options are comparable. A PR greater than 1 indicates that the release to the environment is greater under Scenario 1 and, therefore, that Scenario 2 is a better scenario and installing double bottoms at the facility is a better option for protection of the environment than installing a liner in the facility while leaving the tank bottom untouched. The use of PR allows the owner to measure the level of risk he is willing to assume when considering retrofitting options.

## EXAMPLE

The methodology discussed above is applied to a tank farm located inland in the Pacific Northwest. The tank farm includes 7 tanks storing refined petroleum product. The following information is available about the terminal:

**TABLE 5: INFORMATION ABOUT SITE**

<b>Secondary Containment Areas:</b> Total Area: 140,000ft <sup>2</sup> Open Area: 83,000ft <sup>2</sup> Area of Tank Bottom: 57,000ft <sup>2</sup> Height of Dikes: 5ft	<b>Largest Tank:</b> Diameter: 120 ft Safe Fill Height: 46ft Volume: $\geq$ 93,000 bbls
<b>Soil:</b> Homogenous Sand Deposit $k = 10^{-5}$ m/sec Thickness > 100ft Groundwater Depth: 50ft	<b>Tank Bottoms:</b> Average pinhole diameter $d = 1$ mm (0.04 in.) Average number of pinholes: 1/acre of bottom

Table 4 shows the ranking of the liner options for the facility. The ranking shows that a geomembrane is the preferred liner option. The second step is to compare installation of a geomembrane at the facility versus retrofitting the tanks by installing double bottoms with leak detection systems, a system of overfill protection at the terminal, and a spill recovery system. The spill recovery system consists of a pump with a pumping capacity of 2,500 gpm that can be activated in no less than 6 hours after a catastrophic spill has occurred.

The performance ratio PR discussed above is evaluated in the following. The volume of petroleum product,  $V_1$  that will be released to the environment on an annual basis when geomembranes are installed in the open area and the single bottoms are left unchanged is given as:

$$V_1 = (\text{Leakage Rate through Single Bottom}) \times (\text{Area of Single Bottom}) \times (\text{Time})$$

Using the Giroud et al. method (Giroud et al., 1997), the leakage rate is evaluated as a function of product height. Figure 3 shows flow in gallon/day as function of product height ranging from 0 to 50 ft. Under the product fill height of 46 ft in the tank, the leakage rate is 167 gallons per day (gpd) per acre.

$$V_1 = (167 \text{ gpd/acre}) * (57,000 \text{ ft}^2 / 43.560 \text{ ft}^2/\text{acre}) * (365 \text{ days/year}) / (42 \text{ gallons/bbl})$$
$$V_1 = 1899 \text{ bbls/year}$$

The volume of petroleum product,  $V_2$  that will be released to the environment on an annual basis when double bottoms are installed in each AST and the open area within the secondary containment area is left unchanged is given as:

$$V_2 = (\text{Leakage Rate through Double Bottom}) \times (\text{Area of Double Bottom}) \times (\text{Time}) + (\text{Volume of Product Infiltrated in Soil})$$

following the catastrophic spill.

For a double bottom tank, we assume that there is about 0.5 in of product that may have gone undetected by the leak detection system on top of the original old bottom. Therefore we assumed that there is 0.5 in. of head driving the flow out of the double bottom system. Under this assumption the flow is about 2.88 gpd/acre (Figure 2).

The volume of product infiltrated in the ground is estimated using the numerical model XSLIM (eXpanded Soil Liner Infiltration Model) (Myers et al, 2001) developed to assess the effectiveness of soil liners in controlling hypothetical catastrophic spills in secondary containment areas. XSLIM simulates penetration of petroleum product into the soil liner and the underlying vadose zone. In addition, XSLIM takes into account the response time from the operators, the pumping rate, and the decreasing ponding height of petroleum product as it is recovered from the secondary containment area. The calculated depth of infiltration of product in the ground is 0.54ft. Consequently the volume of product infiltrated in the ground is equal to the depth times the area times the porosity of the soil:

$$\begin{aligned} V_2 &= (2.88) * (57000/43560)*(365 \text{ days/year})/(42 \text{ gallons/bbl}) + \\ &(0.54\text{ft})*(83,000\text{ft}^2)/(5.6\text{ft}^3/\text{bbl})*(0.35) \\ V_2 &= 2801\text{bbls} + 32.8 \text{ bbls/year} \end{aligned}$$

To compare the two retrofitting option the performance ratio defined as:

$$PR = V_1 / V_2$$

is evaluated as a function of time and plotted in Figure 4. Figure 4 shows that the performance ratio is one at 1.5 years. This indicates that unless the return period of a catastrophic failure of the largest tank containing 93,000 bbls is less than 1.5 years then installing double bottoms in the seven tanks at the tank farms provide better protection of the environment. The performance ratio was calculated assuming a defect size of 0.5mm and is reported in Figure 4. Figure 4 indicates that the PR is equals 1 after 6 years. Unless a catastrophic spill occurs every 6 years, a better protection of the environment is obtained retrofitting the tank bottoms rather than placing a liner at the facility and leaving the tank bottom untouched.

## CONCLUSION

This paper presented a methodology to select the optimum engineering alternative at bulk storage facilities. The methodology provides tools to select the optimum liner option and tools to compare the liner option to alternative approach to secondary containment lining. The methodology was applied to an example and it was shown that for the site-specific conditions of the facility the optimum engineering alternative to protect the environment is to install double bottom in the tanks with an overfill protection system.

The opinions expressed in this paper are those of the authors and one should not assume endorsement by the US EPA.

## REFERENCES

- American Petroleum Institute (1997), "Liquid Release Prevention and Detection Measures for Aboveground Storage Tanks, Publication Number 340, October.
- Cutter Information Corporation (1999), Oil Spill Response Reference Guide.
- Giroud, J.P., and Bonaparte, R. (1989), "Leakage Through Liners Constructed with Geomembranes – Part II Composite Liners," Geotextiles and Geomembranes, pages 79-111.
- Giroud, J.P., King, T.D., Sanglerat, T.R., Hadj-Hamou, T. and Khire, M.V. (1997), "Evaluation of the Rate of Liquid Migration Through Defects of a Geomembrane Placed on a Semi-Permeable Soil", Geosynthetics International, Vol. 4., Nos. 3-4, pp.349-372
- King, T.D., Haffner, J., Sanglerat, T.R., Hadj-Hamou, T. and Williamson, T.A. (1997), "Aboveground Storage Tank (AST) Secondary Containment Enhancement", American Petroleum Institute 62<sup>nd</sup> Spring Refining Meeting, Environmental Symposium, San Diego, 7-9 April.

Laine, D.L. (1991), "Analysis of Pinhole Seam Leaks Located in Geomembrane liners Using the Electrical Leak Location Method – Case Histories," Proceedings of Geosynthetics 1991, Volume 1, pp. 239-253, Atlanta.

Myers, P., Luccioni, L., Palmer, B., Hadj-Hamou, T., and Sanglerat, T.R. (2001), "Sufficiently Impervious Secondary Containment for AST's," Proceedings of 21st Annual International Operating Conference and Trade Show, Independent Liquid Terminals Association, Houston, Texas, 11-14 June.

National Fire Protection Association (1993), Flammable and Combustible Liquids Code, NFPA 30.

United States Environmental Protection Agency (1996), EPA Liner Study, Report to Congress, Section 4113(a) of the Oil Pollution Act of 1990, OSWER 9380.0-24, EPA 540/R95/041, PB 95-963538, May.

**TABLE 4: RANKING OF LINER OPTIONS FOR SITE EXAMPLE**

CRITERIA	GENERAL DESCRIPTION	COMMENTS	GRADE	Spray-On Liners		Compacted Clay		Concrete		Asphalt	
				Geosynthetic Clay Liner	GCL	Liquid polymer is sprayed onto a nonwoven geotextile that is placed on a prepared soil surface. Result is a geomembrane-like barrier. Types commonly used today include polyurea and polyurethane.	Fine-grained soil is moisture conditioned and compacted to produce a low-permeability barrier. Material is typically compacted in 6-in. lifts, with total compacted thickness on the order of 2 ft.	Reinforced concrete slab is constructed to form a moisture barrier.	Two layers of asphalt sandwiching a resin-soaked nonwoven geotextile fabric; fabric is the primary permeability barrier.	Comments	Grade
Site Conditions	Silty sand with some boulders, water table is approximately 50 and deep	Boulders will need to be removed or covered, especially if a geomembrane-type GCL is used. Regrading is needed to make tanks the highest points within the diked areas	B	Boulders will need to be removed or covered. Regrading is needed to make tanks the highest points within the diked areas	B	Regrading is needed to make tanks the highest points within the diked areas	B	Regrading is needed to lower the diked areas; some subgrade preparation may also be required	C	Regrading is needed to lower the diked areas; some subgrade preparation may also be required	C
Geometry	Site is flat with available open space for construction operations and staging	Plenty of open space for construction at site, intermediate dikes may be removed to facilitate construction	A	Plenty of open space for construction at site, intermediate dikes may be removed to facilitate construction	A	Plenty of open space for construction at site, intermediate dikes may be removed to facilitate construction	A	Plenty of open space for construction at site, intermediate dikes may be removed to facilitate construction	A	Plenty of open space for construction at site; intermediate dikes may be removed to facilitate construction	A
Penetrations	Penetrations to be sealed include tank bottom chime, 3-ft deep foundations, pumps and at tank edge concrete pipe foundations, and cathodic protection boxes; generally less than 10 penetrations per tank	Boots and seals required for pipeline foundations, pumps and at tank edge	B	Requires proper construction with bentonite seals at pipeline foundations and around tank edge	B	Excellent method for sealing penetrations around pipeline foundations and around tank base	A	Requires proper construction with bentonite seals	B	Boots or gaskets will be required around pipeline foundations and around tank base	B
Regulatory Acceptance Requirements	Federal and State	Very likely (proven technology)	A	Very likely (proven technology)	A	Very likely (proven technology)	A	Very likely (proven technology)	A	Likely effective, but novel approach	B

**TABLE 4: RANKING OF LINER OPTIONS FOR SITE EXAMPLE (continued)**

Engineering Design	Geomembrane	Geosynthetic Clay Liner	Spray-On Liners	Compacted Clay	Concrete	Asphalt
Product Compatibility	Tanks contain common petroleum hydrocarbon products Limited reduction in strength properties after exposure to hydrocarbons for most geomembrane types. Reduced strength estimates can be used for design (i.e. puncture resistance, weld strength, etc.).	B Not significantly impacted by exposure to hydrocarbons if hydrated	B Not of concern with polyurethane; of minor concern with polyethylene	B If soil is dry when exposed to hydrocarbons, permeability will be high; soil should remain hydrated	C Not of concern	A Released product will partially deteriorate the asphalt
Dessication Resistance	Average annual precipitation is 17 in.; driest months are July, August and September (average monthly precipitation is less than 1 inch)	A Not of concern	C Dessication will increase permeability to an unacceptable level; GCL must remain hydrated; irrigation may be required in summer months	A Dessication will increase permeability in higher-plasticity materials; irrigation may be required in summer months	C Not of concern	A Volatile fraction in asphalt will evaporate with time; may induce some cracking
Freeze Thaw Resistance	Five months out of the year (November-March) have average high and low temperatures that are above and below freezing	A Not of concern	B GCL recovers from freeze-thaw cycles	A May induce microcracking and reduce surficial permeability	C Freeze-thaw may worsen existing cracking	C Freeze-thaw may worsen existing cracking
Temperature Extremes	Difference between average annual high and low temperature is 61 degrees; difference between all-time high and all-time low is 133 degrees	B Not of concern	A Some polyurethanes may become brittle at low temperatures	A Temperature extremes may induce cracking	C Temperature extremes may induce cracking	C Temperature extremes may induce cracking
Wind Resistance	Windiest months are March and April (average wind speed = 13 mph)	A Not of concern	A Requires anchoring at pilings; ballast in open areas may also be required	B Not of concern	A Not of concern	A Not of concern
Ultraviolet	Summest months are	A Not of concern	A Limited Concern	B Not of concern	A Not of concern	A Not of concern

TABLE 4: RANKING OF LINER OPTIONS FOR SITE EXAMPLE (continued)

	Geomembrane	Geosynthetic Clay Liner	Spray-On Liners	Compacted Clay	Concrete	Asphalt
Resistance	July and August, with 80% average possibility of sunshine and 16 clear days per month					
Fire Resistance	Not of concern	A	Not of concern	A	Generally flammable, but flame-retardant polyurethanes are available	B
Operator Issues						
Construction	Maintenance will include periodic inspection and repair of liners at facility	C	Easily repaired; but needs to remain covered and hydrated with soil cover	C	Repair requires training of personnel, but repair kits can be used	B
Operational Flexibility	Typical operations includes painting, snow removal, tank cleaning, and tank vac truck operation	B	Vehicular access restriction is reduced by the cover soil, but there will still be size limits for vehicles	B	Access to tanks will be restricted unless the liner is protected with a layer of cover soil	B
Stormwater Management	Average precipitation is 17 in./yr; wettest month is December (2.3 in/month); wettest month on record was 5.7 in.; sheen on water will require treatment from impacted soil	B	Good flow along geomembrane surface; need to minimize ponding near tank; sheen on water may result from impacted soil	C	Flow is slower than geomembrane; need to minimize ponding near tank; sheen on water may result from impacted soil	A
Clean-Up	Spills may occur due to overfills; unzipping spill is considered highly unlikely	C	Geomembrane may be damaged during cleanup operations; cover soil will need to be removed	B	May be damaged during cleanup	B
Subsurface Remediation	BTEX, MBE, and others were not detected above threshold cleanup levels at either site in	C	Requires significant effort to remove for access to underlying soil and repair afterwards	B	Easy to remove for access to underlying soil	B
					Underlying soil is accessible with minor excavation	B
					Significant effort required to remove the concrete for access to underlying soil	C
					Significant effort required to repair after removal	C

TABLE 4: RANKING OF LINER OPTIONS FOR SITE EXAMPLE (continued)

	Geomembrane	Geosynthetic Clay Liner	Spray-On Liners	Compacted Clay	Concrete	Asphalt
recent monitoring reports; remediation is not considered necessary at this time		buried geomembrane cover				
Trafficability	Vehicles require access to and around the perimeter of the tanks	B Traficable if cushioned and covered	B Will restrict vehicular access to tanks; trafficable if cushioned and covered	C Trafficable under dry conditions	B Not of concern	A Not of concern
Vegetation Control	Containment areas are periodically sprayed for will reduce the potential for root penetration	B Essential	C Not of concern	A Essential for proper performance	C Not of concern if cracks are sealed	B Not of concern if cracks are sealed
Costs	Capital cost per square foot (not used for comparison purposes only and not including engineering and CQA) Preliminary costs to be used for comparison purposes only and not for bid preparation; these costs will need to be refined prior to bid preparation	Moderate to high -- \$2.80 - 4.30 (includes geotextile cushion, boots, sealing around tank, and 1-ft protective cover soil)	C Moderate -- \$2.60 - 3.40 (includes geotextile cushion and 1-ft protective cover soil)	C High -- \$4.00 - 7.00 (range for flexible and rigid type polyurethanes)	D Low to moderate -- \$1.70 - 4.00 (for 2-ft thick layer; increase cost for hauling distances greater than 20 miles; total cost includes grading of existing surface, hauling, spreading and compaction)	C High -- \$5.00 - 6.60 (for 6 to 8-in. reinforced slab)
Maintenance	Maintenance may include dewatering, period inspections and repairs at each terminal overfills; unzipping spill is considered highly unlikely	Low (should prevent plant growth)	B Moderate (GCL must remain hydrated)	C Low (repair kits are available)	B Low (must prevent plant growth)	B Low (periodic inspection and crack sealing)
Clean-Up	Spills may occur due to overfills; unzipping	High (removal of cover soil and possible repair of geomembrane)	D High (removal of cover soil and replacement of GCL)	D Low (some repair may be required)	D High (due to soil removal)	D Low
Remediation	BTEX, MBE, and others were not detected above threshold cleanup levels at either site in recent monitoring reports	High (due to removal of soil and geomembrane and repair of geomembrane)	D Moderate (due to removal of cover soil and repair of GCL)	C Moderate (removal and repair of cover required)	B Low	B High (removal of concrete required)
Overall Performance	Excellent	A Excellent	A Excellent	A Excellent	A Excellent	A Excellent


**TABLE 4: RANKING OF LINER OPTIONS FOR SITE EXAMPLE (continued)**

Overall Reliability	Geomembrane	Geomembrane			Geosynthetic Clay Liner			Spray-On Liners			Compacted Clay			Concrete			Asphalt		
		Good	Average	B	C	Good	Average	B	Average	C	High construction costs, potential for cracking, and cleanup effort	Average	C	Average	C	Average	C		
Critical Performance and Reliability Issues	Proper construction and COA are important to achieve acceptable performance; potentially high cleanup costs	GCL must be initially confined and hydrated remain confined and hydrated to perform properly; potentially high cleanup costs	Susceptibility to damage (although not as susceptible as a geomembrane) and cost	Susceptible to desiccation cracking; potentially high cleanup costs; high soil procurement costs may prohibit this option	High construction costs, potential for cracking, and cleanup effort														
COMMENTS	This is an effective, reliable liner that can be constructed at a moderate cost and impose less hindrance to operations than the exposed geomembrane	This is an effective liner, but it must remain confined and hydrated to perform properly	This liner is durable, reliable, and excellent for odd geometries, but somewhat expensive	This is an effective liner, but may desiccate if not hydrated; procurement costs could be high	This liner is effective, but susceptible to chemical attack during a spill														
RANK		<b>1</b>		<b>2</b>		<b>3</b>		<b>4</b>		<b>5</b>		<b>6</b>		<b>7</b>					

FIGURE 1: TYPICAL SECONDARY CONTAINMENTS



FIGURE 2: DEFECTS IN GEOMEMBRANES

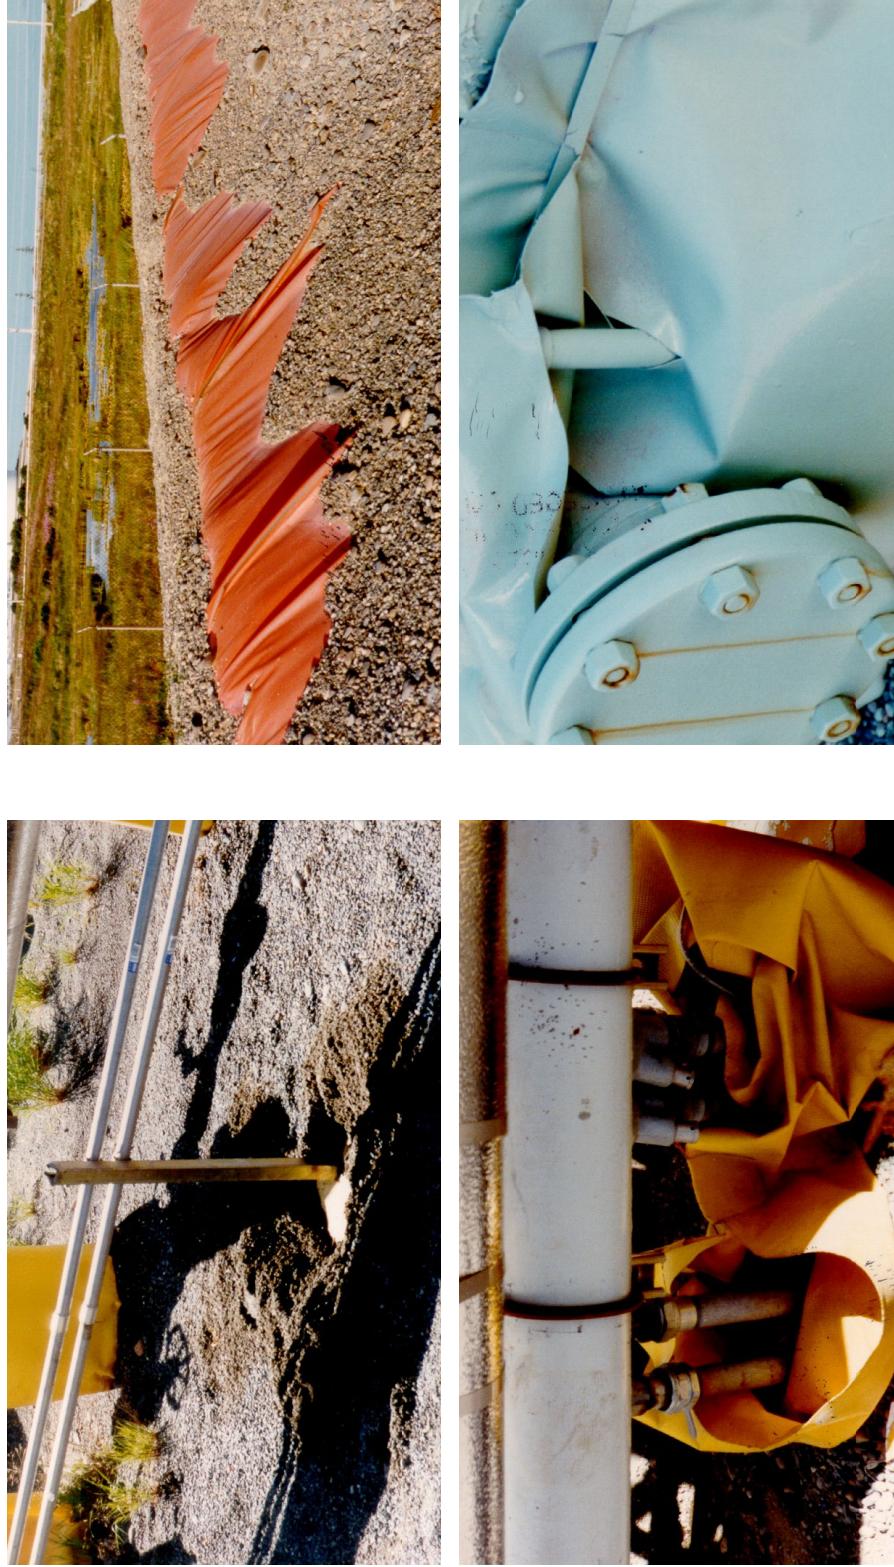

THH/AST/HADJ-HAMOUPAPER.DOC

02 07 08/15:50

FIGURE 3: LEAKAGE RATE THROUGH DEFECT IN TANK BOTTOM

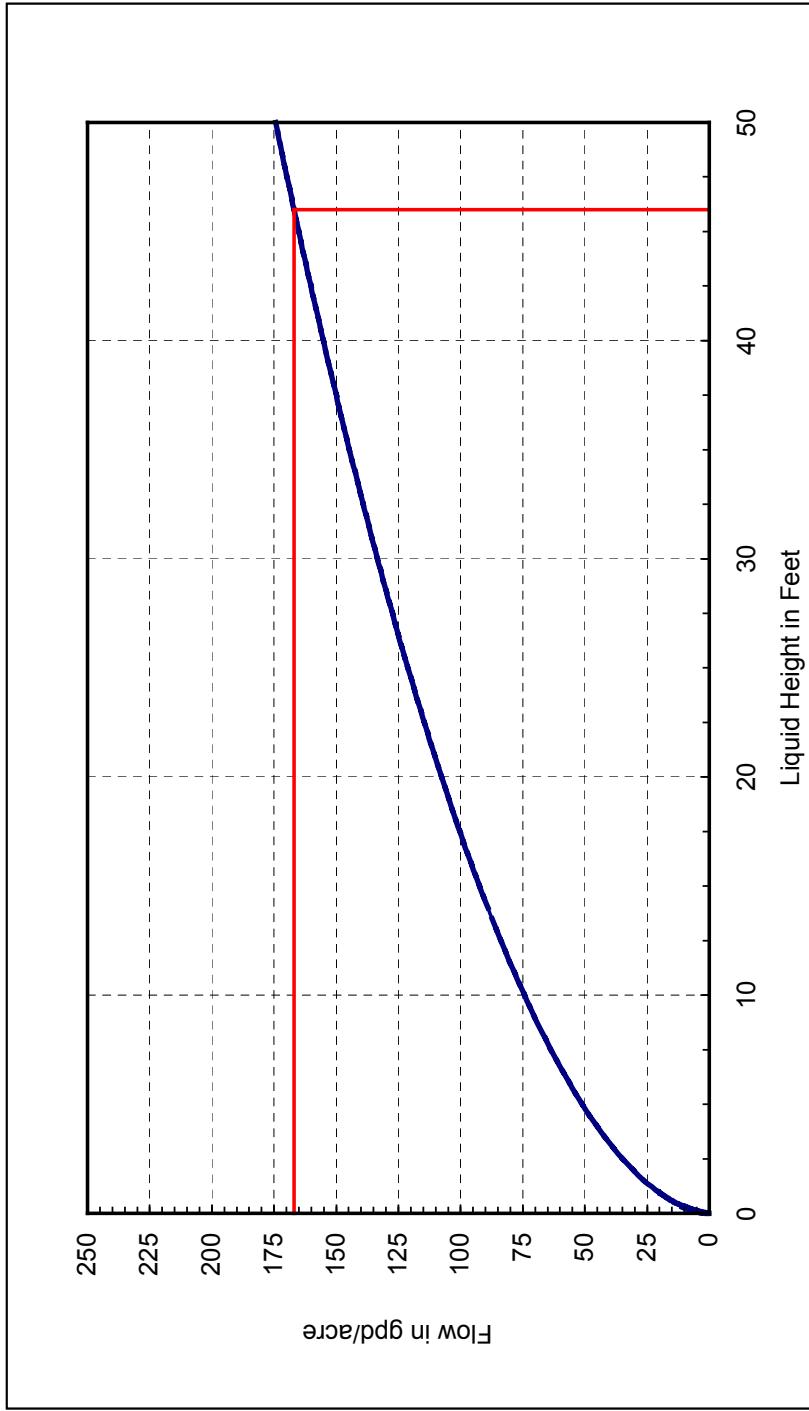


FIGURE 4: PERFORMANCE RATIO

